

Charged Vortices in High Temperature Superconductors Probed by NMR

Ken-ichi Kumagai^{1,3}, Koji Nozaki¹ and Yuji Matsuda^{2,3}

¹ *Division of Physics, Graduate School of Science, Hokkaido University, Kita-ku, Sapporo 060-0810, Japan*

² *Institute for Solid State Physics, University of Tokyo, Kashiwanoha, 5-1-5, Kashiwa, Chiba 277-8581, Japan*

³ *CREST, Japan Science and Technology Corporation, Kawaguchi, Saitama 332-0012, Japan*

(received)

We report a first experimental evidence that a vortex in the high temperature superconductors (HTSC) traps a finite electric charge from the high resolution measurements of the nuclear quadrupole frequencies. In slightly overdoped $\text{YBa}_2\text{Cu}_3\text{O}_7$ the vortex is negatively charged by trapping electrons, while in underdoped $\text{YBa}_2\text{Cu}_4\text{O}_8$ it is positively charged by expelling electrons. The sign of the trapped charge is opposite to the sign predicted by the conventional BCS theory. Moreover, in both materials, the deviation of the magnitude of the charge from the theory is also significant. These unexpected features can be attributed to the novel electronic structure of the vortex in HTSC.

I. INTRODUCTION

One of the most important physical properties of the vortex created in the type-II superconductors is that a vortex line can support a magnetic flux with a flux quantum $\Phi_0 = hc/2e (= 2.07 \times 10^{-7} \text{ Oe}\cdot\text{cm}^2)^1$. This fact has been confirmed experimentally more than 4 decades ago. On the other hand, it is only very recent that another prominent feature, namely the possibility that a vortex of the superconductor can accumulate a finite electric charge as well, has come to be realized²⁻⁵. The vortex charge appears as a result of the chemical potential difference between the vortex core and the region away from the vortex core. It should be emphasized that the sign and magnitude of this charge is closely related to the microscopic electronic structure of the vortex, which in turn reflects all the fundamental natures of the superfluid electrons and the low energy excitation out of the condensate. Moreover, it has also been pointed out recently that the vortex charge strongly affects the dynamical properties of the vortex⁶⁻¹⁰. For instance, the origin of the vortex Hall anomaly has been attributed to the vortex charge. Though the clarification of the issue of the vortex charge serves as an important test of the predictions for the vortex electronic structure and the dynamics, it has never been examined experimentally so far. This is mainly because in conventional superconductors the magnitude of the accumulated charge within the core is very small and is extremely difficult to observe.

In this paper we report a first straightforward attempt to identify the vortex charge in the high temperature superconductors (HTSC) by high resolution measurements of the nuclear quadrupole frequency ν_Q , which is very sensitive to the local charge density. We show that a vortex in HTSC indeed traps a small but finite electronic charge as well. In slightly overdoped $\text{YBa}_2\text{Cu}_3\text{O}_7$ the vortex is negatively charged, while in underdoped $\text{YBa}_2\text{Cu}_4\text{O}_8$ it is positively charged. The sign of the trapped charge is opposite to the sign predicted by the conventional BCS theory. Moreover, in both materials,

the accumulated charge is much larger than expected in the ordinary superconductors. We discuss several possible origins for these discrepancies.

II. VORTEX CHARGE

We first briefly introduce the vortex charge in type-II superconductors. In the core of the conventional superconductors, the distance between each discrete energy levels of the quasiparticles in the Andreev bound states are merely of the order of a few mK. Thus it is sufficient to view the energy levels as forming a continuous spectrum, just like in a normal metallic state^{1,11}. Generally the chemical potential μ in the superconducting state differs from that in the normal state, if an electron-hole asymmetry is present. Assuming therefore that the vortex core is a normal metallic region surrounded by the superconducting materials, this difference in μ is expected to arise and should lead to the redistribution of the electrons. In order to maintain the same electrochemical potential on both side, the charge transfer occurs between the core and the outside.

In the framework of the BCS theory taking into account the metallic screening effect, the charge accumulated within the vortex core Q_ξ per layer normal to the magnetic field is given as,

$$Q_\xi \approx \frac{2ek_F s}{\pi^3} \left(\frac{\lambda_{TF}}{\xi} \right)^2 \left(\frac{d \ln T_c}{d \ln \mu} \right), \quad (1)$$

where λ_{TF} is the Thomas-Fermi screening length, s is the interlayer distance, μ is the chemical potential and $e(>0)$ is the electron charge³. The sign of the core charge is determined by $d \ln T_c / d \ln \mu$, which represents the electron-hole asymmetry. Outside the core, the charges with opposite sign screen the core charge, similar to a charged particle in a metal. Far outside the core, this screening charges decay gradually with a power law dependence as r^{-4} (see Fig.1 (a))^{3,9}. In strong fields ($H_{c1} \ll H \ll H_{c2}$),

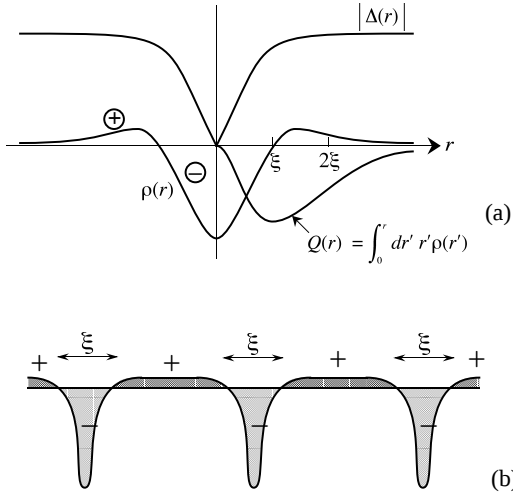


FIG. 1. (a): Schematic figure of the charge distribution around a single vortex core when the electrons are trapped within the core (negatively charged core). $\Delta(r)$ is the superconducting energy gap. $\rho(r)$ is the charge density. The charge accumulated inside the core are screened by the charges with opposite sign. $\rho(r)$ decays gradually as r^{-4} well outside the core region. $Q(r)$ is the total charge within the distance r . $Q(r)$ goes to zero as $r \rightarrow \infty$ due to the requirement of the overall charge neutrality. (b): The charge density modulation in the strong magnetic field ($H_{c1} \ll H \ll H_{c2}$) where each vortices overlaps.

each vortex overlaps with its neighborhood. Then the charge density outside the core is nearly constant, and the periodic modulation of the charge density appears for the periodic vortex lattice (Fig.1(b)). In ordinary superconductors, $|Q_\xi|$ is estimated to be $\sim 10^{-5} - 10^{-6}e$, using $k_F \sim 1\text{\AA}^{-1}$, $\lambda_{TF} \sim k_F^{-1} \sim 1\text{\AA}$, $\xi \sim 100\text{\AA}$ and $|\ln T_c / d \ln \mu| \approx \ln(\hbar \omega_D / k_B T_c) \sim 1 - 10$, where ω_D is the Debye frequency. Thus $|Q_\xi|$ is negligibly small and is very difficult to observe.

However, the situation in the case of HTSC seems to be promising because ξ is extremely short compared to that of the conventional superconductors. Moreover the strong electron correlation effects and d -wave pairing symmetry of HTSC are expected to change the electronic structure of the vortex dramatically¹²⁻¹⁷. In fact, recent STM measurements revealed that the vortex of HTSC is very different from those of conventional superconductors¹⁸⁻²⁰. These unusual features of HTSC are expected to enhance the charging. We will discuss these issue later.

The vortex charge also plays an important role for the vortex dynamics. When a vortex moves in the superfluid electrons, the core plays a key role in dissipation processes¹⁰. One of the most striking phenomena is the vortex Hall anomaly, namely sign reversal of the flux flow Hall effect below T_c , which is observed in most HTSC²¹. This Hall sign reversal indicates that the vortices move upstream against the superfluid flow. Such an unusual motion has never been observed in any other fluid including superfluid helium and cannot be explained in the

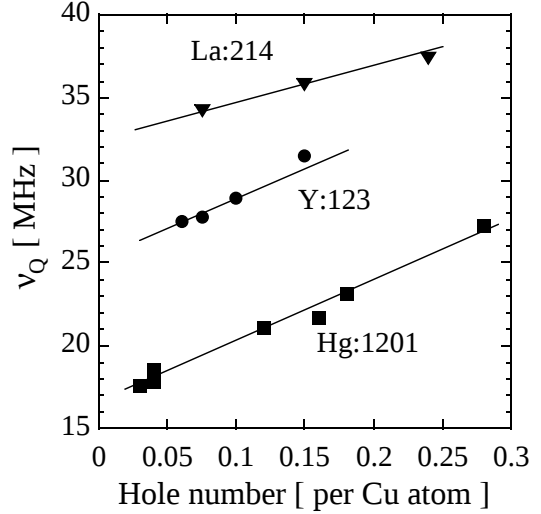


FIG. 2. Doping dependences of ν_Q on the Cu(2) site for $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$,²⁴ $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$,²⁵ and $\text{HgBa}_2\text{CuO}_{4+\delta}$.²⁶ ν_Q is proportional to the hole number.

framework of the classical hydrodynamic theory²². Recently, this phenomena has been discussed in terms of the vortex charge which produces an additional force acting on the vortices⁶⁻⁹.

To elucidate the vortex charge, a direct observation of the local carrier density is strongly required. It has been pointed out by many authors that ν_Q in HTSC is very sensitive to the local hole density²³⁻²⁶. In a solid, an electron distribution with spherical asymmetry such as unclosed $3d$ shell and noncubic surrounding ions induce a local electric field gradient (EFG) in the vicinity of the nuclei. This EFG lifts the degeneracy of the nuclear spin levels, interacting with the nuclear quadrupole moment, Q_N . The relevant information is obtained from the nuclear quadrupole resonance (NQR) in zero magnetic field and the nuclear magnetic resonance (NMR) in a finite magnetic field. For the ^{63}Cu nuclei with spin $I=3/2$, the NQR resonance frequency ν_Q^{NQR} is expressed as

$$\nu_Q^{NQR} = \frac{e^2 Q_N q_{zz}}{2h} \sqrt{1 + \frac{\eta^2}{3}} = \nu_Q \sqrt{1 + \frac{\eta^2}{3}} \quad (2)$$

where eq_{zz} is the largest principle (z -axis) component of EFG at the nuclear site, Q_N ($= -0.211$ barn for ^{63}Cu) is the quadrupole moment of copper nuclei.²⁷ The asymmetry parameter η of the EFG defined as $\eta = |(q_{xx} - q_{yy})/q_{zz}|$ is close to zero for the Cu site in the two dimensional CuO_2 planes (Cu(2) site).

In a strong magnetic field when the Zeeman energy is much larger than the quadrupole energy, each Zeeman level is shifted by the quadrupole interactions and thus, two satellite peaks ($\pm 3/2 \leftrightarrow \pm 1/2$) appear on both sides of the central ($\pm 1/2 \leftrightarrow \mp 1/2$) resonance peak. The frequency difference between the upper and the lower satellites exactly coincides with $2\nu_Q$, when a magnetic field is applied parallel to the largest principle axis of EFG, namely, $H \parallel c$ -axis in the present experimental

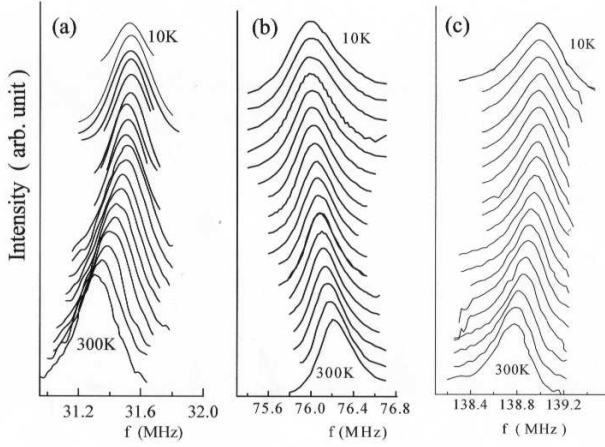


FIG. 3. The NQR (a), the lower (b) and the upper (c) NMR satellite spectra at 9.4T for $^{63}\text{Cu}(2)$ site of $\text{YBa}_2\text{Cu}_3\text{O}_7$ for various temperatures. (220K, 200K, 180K and 160K to 10K by a 10K step.)

condition described below. Even for the second order or more higher order quadrupole effect in the presence of the asymmetry η of EFG, the each satellite line shifted as much and the corrections for $2\nu_Q$ are vanishing in the case of $H \parallel c$ -axis.²⁷

Generally the EFG originates from two different sources, namely from the on-site distributions $q_{\text{on-site}}$ of the electrons and from the surrounding ions q_{ion} , $q = q_{\text{on-site}} + q_{\text{ion}}$. Recent analysis of q on the Cu(2) site suggests that $q_{\text{on-site}}$ is mainly composed of the Cu 4p and 3d shell terms²³. In HTSC the holes in the Cu $3d_{x^2-y^2}$ orbital play an important role for the onset of superconductivity. Figure 2 shows the doping dependence of ν_Q of the Cu(2) site for $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ ²⁴, $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ ²⁵, and $\text{HfBa}_2\text{CuO}_{4+\delta}$ ²⁶. In all materials, ν_Q increases linearly with the number of holes in the planes and can be written as,

$$\nu_Q = A n_{\text{hole}} + C, \quad (3)$$

where n_{hole} is the number of holes per Cu(2) atom, and A and C are constants²⁴⁻²⁶. Although C is strongly material dependent, reflecting the difference in ν_{ion} , $A \approx 20 - 30$ MHz per hole for the Cu(2) atom is essentially material independent. Thus, the precise measurement of ν_Q makes possible an accurate determination of the change of the local hole number at the Cu site.

III. EXPERIMENTAL

The principle of our experiment is the following. In the measurement, only the resonance of the $^{63}\text{Cu}(2)$ nuclei *outside the vortex core* is detected. This is because the applied field is much less than H_{c2} and hence the core region occupies a smaller area in the sample. If the vortex core traps (expels) a finite amount of electrons, the electron

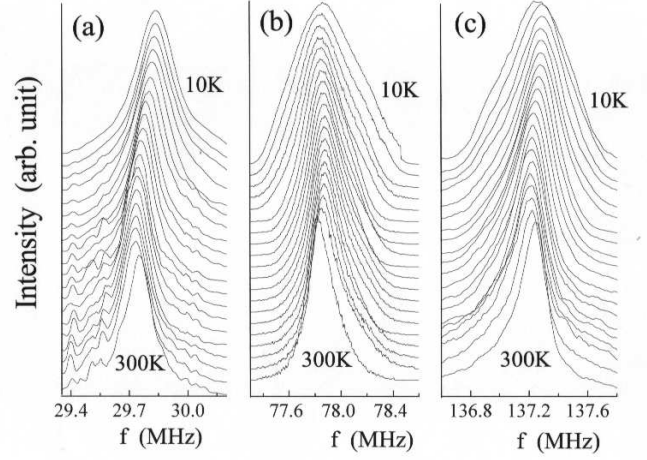


FIG. 4. The NQR in zero field (a) and the lower (b) and the upper (c) NMR-satellite spectra at 9.4T for $^{63}\text{Cu}(2)$ site of $\text{YBa}_2\text{Cu}_4\text{O}_8$ for various temperatures. (300K, 220K, 200K, 180K and 160K to 10K by a 10K step.)

density outside the core should decrease (increase) from that in zero field where the electron distribution is uniform, as shown in Fig.1(b). We are able to detect the change of carrier density through the change of the value of ν_Q .

In the present measurements, we used slightly overdoped $\text{YBa}_2\text{Cu}_3\text{O}_7$ and underdoped $\text{YBa}_2\text{Cu}_4\text{O}_8$ in which the NQR and NMR spectra are very sharp compared to those of other HTSC. The NMR spectra are obtained for fine powdered sample (the grains are less than $33 \mu\text{m}$) with uni-axial alignment. The each grain aligns to an easy axis (the c -axis) in a high external field at room temperature, and then fixed with epoxy (Stycast 1266).

The Cu-NQR and NMR spectra were obtained by a conventional pulse spectrometer. The NMR experiments were performed in the field cooling condition under a constant field of 9.4T by using a highly-homogeneous superconducting magnet which was stabilized to less than 1ppm during the experiment. The present measurement in the vortex state is made in the so-called Bragg-glass phase in which the quasi-long-range order of the vortex lattice is preserved. We see slightly-asymmetric shape of the NMR-satellite spectra due to the somehow misalignment of some grains. The line broadenings of the NQR spectra in zero external field are not observed even below T_c in both $\text{YBa}_2\text{Cu}_3\text{O}_7$ and $\text{YBa}_2\text{Cu}_4\text{O}_8$. The width of the NMR spectra becomes broader with decreasing T below T_c partly due to the magnetic field inhomogeneity caused by the introduction of the vortices and partly due to the spatial distribution of carrier density, which we will discuss later.

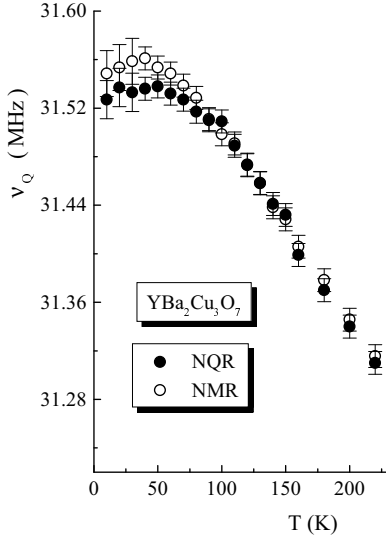


FIG. 5. The temperature dependence of ν_Q obtained from NQR and NMR for $^{63}\text{Cu}(2)$ site of $\text{YBa}_2\text{Cu}_3\text{O}_7$.

IV. RESULTS AND DISCUSSION

Figure 3 shows the NQR and lower and upper satellite spectra of $^{63}\text{Cu}(2)$ NMR for optimum doped $\text{YBa}_2\text{Cu}_3\text{O}_7$. Figure 4 shows also the NQR and NMR spectra of $^{63}\text{Cu}(2)$ site of $\text{YBa}_2\text{Cu}_4\text{O}_8$. All data were taken by utilizing a phase coherent spin echo spectrometer. The spectra are obtained with a superposed method of the Fourier Transform spectra of the spin echo measured at a certain frequency interval. The temperature dependences of ν_Q obtained from NMR and NQR are shown for $\text{YBa}_2\text{Cu}_3\text{O}_7$ and $\text{YBa}_2\text{Cu}_4\text{O}_8$ in Figs. 5 and 6, respectively. The temperature dependences of ν_Q^{NQR} for both $\text{YBa}_2\text{Cu}_3\text{O}_7$ and $\text{YBa}_2\text{Cu}_4\text{O}_8$ are quite similar to those of ν_Q^{NQR} reported previously²⁸. It should be noted that the procedure for obtaining ν_Q from the frequency difference between the upper and the lower satellites is essentially free from the influence of the change of magnetic shift (or Knight shift). Moreover, the magnetic effect of the asymmetric broadening (so-called Redfield pattern) due to the vortex lattice in the superconducting state is exactly cancelled out in the process determining ν_Q from NMR. Thus, we obtained the ν_Q values simply from the difference of the peak frequencies of the two satellite lines.

We plot in Fig. 7 the difference between ν_Q in zero field and in the vortex state, $\Delta\nu_Q = \nu_Q(0) - \nu_Q(H)$, for $\text{YBa}_2\text{Cu}_3\text{O}_7$ and $\text{YBa}_2\text{Cu}_4\text{O}_8$. The ν_Q in zero field for NQR is obtained after the correction by the factor of $\sqrt{1 + \eta^2/3}$ in Eq.(1), although this factor is at most 0.03% of ν_Q for $\eta \approx 0.04$ of the present materials. In both materials $\Delta\nu_Q$ is essentially zero above T_c , indicating no modulation of the carrier density. Meanwhile a

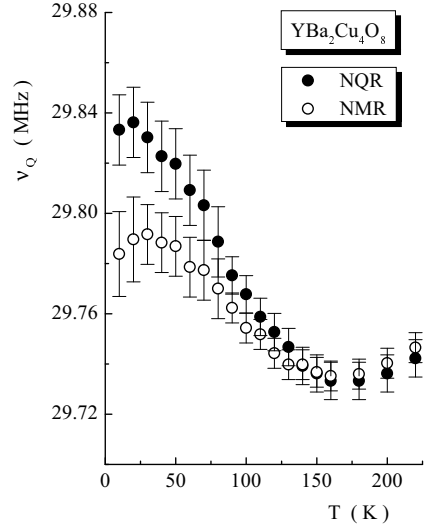


FIG. 6. The temperature dependence of ν_Q obtained from NQR and NMR for $^{63}\text{Cu}(2)$ site of $\text{YBa}_2\text{Cu}_4\text{O}_8$.

nonvanishing $\Delta\nu_Q$ is clearly observed below T_c in both materials. While $\Delta\nu_Q \sim -25\text{kHz}$ is of negative sign and in $\text{YBa}_2\text{Cu}_3\text{O}_7$, $\Delta\nu_Q \sim 50\text{kHz}$ is of positive sign in $\text{YBa}_2\text{Cu}_4\text{O}_8$ at $T=0$.

We discuss here several possible origins for the nonzero $\Delta\nu_Q$. We first point out that the magnetostriction cannot be the origin of the nonzero $\Delta\nu_Q$. In fact, both the magnetostriction and ultrasonic absorption measurements showed that the local lattice distortion $\Delta\ell$ caused by the magnetostriction is negligibly small under the field cooling condition; $\Delta\ell/\ell < 10^{-8}$ below 10 T where ℓ is the lattice constant. We next remark on an in-plane charge modulation caused by a charge stripe formation³⁰ or the charge density wave (CDW) transition of the chain site.^{31,32} Although the static charge ordering associated with a stripe formation has been discussed in some of the high- T_c cuprates, such orderings have never been reported in $\text{YBa}_2\text{Cu}_3\text{O}_7$ nor in $\text{YBa}_2\text{Cu}_4\text{O}_8$. Moreover, it has been reported that in La:214 compounds the static charge stripe order gives rise to the wipe-out of NQR signals³³, implying that the static stripe order, if present, induces a large effects on quadrupole interactions. However, we have not observed the broadening of the NQR spectra (in zero field) and nor any sign of the wipe-out of NQR and NMR signals in the present measurements for $\text{YBa}_2\text{Cu}_3\text{O}_7$ or $\text{YBa}_2\text{Cu}_4\text{O}_8$. Finally we mention a recent report of the broadening of the NQR line widths in the plane at low temperatures in $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$, which was explained in terms of the CDW formation in the chain site.³² In the present study, in which we obtained sharper NQR line widths compared to the previous reports^{31,32}, such line-broadenings due to the electric quadrupole interaction is not observed. Thus there is no evidence of the charge modulation due to CDW or stripe formation

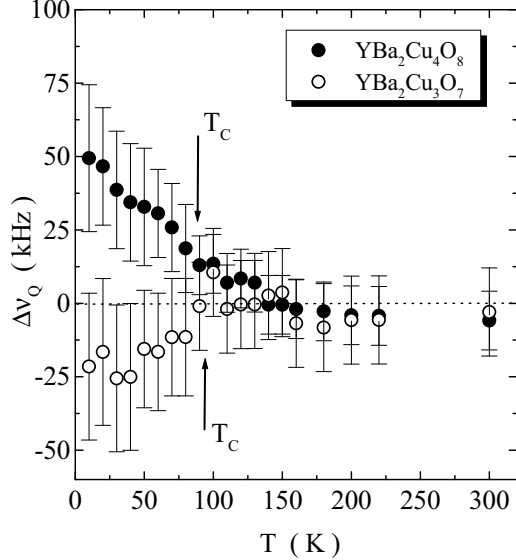


FIG. 7. T -dependence of $\Delta\nu_Q = \nu_Q(0) - \nu_Q(H = 9.4 \text{ T})$ for $\text{YBa}_2\text{Cu}_3\text{O}_7$ and $\text{YBa}_2\text{Cu}_4\text{O}_8$. In both materials nonzero $\Delta\nu_Q$ is clearly observed below T_c , showing that the electron density outside the core differs from that in zero field.

in zero field in our crystals. It is also quite unlikely that the magnetic field induces the CDW or stripe formations. Having ruled out these various possibilities, we conclude that the nonzero values for $\Delta\nu_Q$ naturally lead to the fact that *the electron density outside the vortex core is different from that in zero field*.

We now discuss the issue of the sign and magnitude of the accumulated charge. The negative $\Delta\nu_Q$ in $\text{YBa}_2\text{Cu}_3\text{O}_7$ indicates the increment of the hole density outside the core. This excess density of holes is nothing but the holes expelled from the core. Therefore the accumulated charge in the core of $\text{YBa}_2\text{Cu}_3\text{O}_7$ is negative. By the same reasoning, the positive $\Delta\nu_Q$ in $\text{YBa}_2\text{Cu}_4\text{O}_8$ indicates a positive accumulated charge. Meanwhile, since the chemical potential decreases monotonically with doping holes, Eq.(1), $\text{sgn}Q_\xi = \text{sgn}(d \ln T_c / d \ln \mu)$, predicts that $Q_\xi > 0$ in the underdoped regime while $Q_\xi < 0$ in the overdoped regime. This is strikingly in contrast to the sign determined by the present experiment. The deviation of the magnitude of the charge from theory is also noteworthy. The magnitude of charges per pancake vortex, which are roughly estimated using $Q_\xi \approx \Delta\nu_Q H_{c2} / A H$ assuming $H_{c2} \sim 200 \text{ T}$ are $Q_\xi \sim -0.005e$ to $-0.02e$ for $\text{YBa}_2\text{Cu}_3\text{O}_7$ and $Q_\xi \sim 0.01e$ to $0.05e$ for $\text{YBa}_2\text{Cu}_4\text{O}_8$. However, according to Eq.(1), Q_ξ is estimated to be $\sim 10^{-4} - 10^{-5}e$ where we assumed $\xi \sim 30 \text{ \AA}$. Therefore $|Q_\xi|$ determined by the present experiments are still one or two order of magnitude larger than ex-

pected by Eq.(1). Thus *the BCS theory not only predicts the wrong sign of the charge but also underestimates $|Q_\xi|$ seriously*.

There are several intriguing possible origins for these discrepancies. For example, because of the extremely short ξ , the vortex core may be in the quantum limit $k_F \xi \sim 1$, where k_F is the Fermi wave number. In this limit, the description of the quasiparticles in terms of semiclassical wavepackets breaks down in contrast to conventional superconductors¹³. Furthermore, as suggested by recent theories of the vortex core based on *e.g.* the t - J or SO(5) models, the antiferromagnetic (AF) state may be energetically preferable to the metallic state in the vortex core of HTSC^{14,15,17}. If this is indeed so, the AF correlation is expected to enhance the charging effect because it causes a large shift of μ by changing the density of states of the electrons inside the core dramatically. We note here that the present results exclude the possibility of the SO(5) insulating AF core^{14,17} in which holes should be expelled from the core and the accumulated charges are always negative; the present result yields the opposite sign for $\text{YBa}_2\text{Cu}_4\text{O}_8$ in the underdoped regime where the AF correlation is important. Therefore a detailed microscopic calculation is needed to evaluate the accumulated charge quantitatively including the sign.

V. CONCLUSION

From the precise ^{63}Cu -NMR and NQR measurements, we have shown that a vortex in type-II superconductors can trap a finite electric charge as well as magnetic flux. In the slightly overdoped $\text{YBa}_2\text{Cu}_3\text{O}_7$ the vortex is negatively charged, while in underdoped $\text{YBa}_2\text{Cu}_4\text{O}_8$ it is positively charged. In both high T_c materials, the accumulated charges are much larger than expected in the ordinary superconductors. The sign and value of the charges indicate the novel electronic structure of the vortex in HTSC.

VI. ACKNOWLEDGMENTS

We thank Y. Kato, K. Maki, T. Mishonov, M. Ogata, D. Rainer, E.B. Sonin, M. Takigawa, A. Tanaka, and H. Yasuoka for helpful discussions. We also thank H. Ikuta and T. Hanaguri for comments on the magnetostriction. We also thank S. Shamoto and T. Isobe for their technical assistance on the crystal growth and K. Kakuyanagi for his assistance on NMR measurement. This work was supported by the REIMEI Research Resources of the Japan Atomic Energy Research Institute, Iketani Science and Technology Foundation and a Grant-in-Aid for Scientific Research on Priority Area "Vortex Electronics" from the Ministry of Education, Science, Sports and Culture of Japan.

-
- ¹ P.G. de Gennes in *Superconductivity of Metals and Alloys*. (Addison-Wesley Publishing Co., Inc., 1989)
- ² D.I. Khomskii and A. Freimuth, Phys. Rev. Lett. **75** 1384 (1995).
- ³ G. Blatter *et al.*, Phys. Rev. Lett. **77**, 566 (1996).
- ⁴ T. Mishonov, cond-mat/0004286.
- ⁵ H. Hayashi *et al.*, J. Phys. Soc. Jpn. **67** 3368 (1999).
- ⁶ A.T. Dorsey *et al.*, Phys. Rev. B **46**, 8376 (1992), N.B. Kopnin, and A.V. Lopatin, Phys. Rev. B **51**, 15291 (1995).
- ⁷ A. van Otterlo *et al.*, Phys. Rev. Lett., **75**, 3736 (1995).
- ⁸ M. V. Feigel'man *et al.*, JETP Lett., **62**, 834 (1995).
- ⁹ Y. Kato, J. Phys. Soc. Jpn. **68**, 3798 (1999).
- ¹⁰ M. Eschrig *et al.*, Phys. Rev. B **60**, 10447 (1999).
- ¹¹ F. Gygi, and M. Schlüter, Phys. Rev. B **43**, 7609 (1991).
- ¹² N. Schopohl, and K. Maki, Phys. Rev. B **52**, 490 (1995).
- ¹³ Y. Morita *et al.*, Phys. Rev. Lett. **78**, 4841 (1997).
- ¹⁴ D.P. Arovas *et al.*, Phys. Rev. Lett. **79**, 2871 (1997).
- ¹⁵ A. Himeda *et al.*, J. Phys. Soc. Jpn. **66** 3367 (1997).
- ¹⁶ M. Franz, and Z. Tesanovic, Phys. Rev. Lett. **80**, 4763 (1998).
- ¹⁷ B.M. Andersen *et al.*, Phys. Rev. B, **61**, 6298 (2000).
- ¹⁸ I. Maggio-Aprile *et al.*, Phys. Rev. Lett. **75**, 2754 (1995).
- ¹⁹ Ch. Rennner *et al.*, Phys. Rev. Lett. **80**, 3606 (1998).
- ²⁰ S.H. Pan *et al.*, Phys. Rev. Lett. **85**, 1536 (2000).
- ²¹ T. Nagaoka *et al.*, Phys. Rev. Lett. **80**, 3594 (1998) and references therein.
- ²² J. Bardeen and M.J. Stephen, Phys. Rev. **140**, A1197 (1965), P. Nozières and W.F. Vinen, Phys. Mag. **14**, 667 (1966).
- ²³ K. Schwarz, Phys. Rev. B, **42**, 2051 (1990), Y. Ohta *et al.* J. Phys. Soc. Jpn. **61**, 2198 (1992)
- ²⁴ H. Yasuoka, in *Spectroscopy of Mott Insulator and Correlated Metals*, edited by A. Fujimori and Y. Tokura p.213 (Springer Series in Solid-State Sciences, Vol.119).
- ²⁵ G. Zheng *et al.*, J. Phys. Soc. Jpn. **64**, 2524 (1995).
- ²⁶ A.A. Gippius *et al.*, Phys. C **276**, 57 (1997).
- ²⁷ G.C. Cater *et al.* in *Metallic Shifts in NMR* (Pergamon Press 1977).
- ²⁸ K. Müller *et al.*, Physica C **162-164**, 173 (1989), A. Suter, *et al.*, Phys. Rev. B **56**, 5542 (1997).
- ²⁹ H. Ikuta *et al.*, Phys. Rev. Lett. **70**, 2166 (1993). T. Hagiaguri, private communication.
- ³⁰ J.M. Tranquada, *et al.*, Nature **375**, 561 (1995).
- ³¹ S. Kramer, M. Meisinger, Phys. Rev. Lett. **83**, 396 (1999), and **85** 1637 (2000).
- ³² B. Grevin, Y. Berthier and G. Collin, Phys. Rev. Lett. **85**, 1310 (2000), and **84**, 1636 (2000).
- ³³ A.W. Hunt, *et al.*, Phys. Rev. Lett. **82**, 4300 (1999).